



Teflon™ PTFE NXT 70

Modified Granular Fluoroplastic Resin

Product Information

Description

Teflon™ PTFE NXT 70 is a chemically modified PTFE polymer. When properly processed, it offers an excellent combination of properties that are characteristic of Teflon™ fluoroplastic resins:

- Chemical inertness
- Exceptional dielectric properties
- Heat resistance
- Toughness and flexibility
- Low coefficient of friction
- Non-stick characteristics
- Negligible water absorption
- Excellent weather resistance

In addition, this resin offers weldability, improved resistance to deformation under load, increased resistance to permeation of chemicals, and a higher dielectric breakdown voltage. It exhibits minimal sagging in billets as large as 350 kg (800 lb).

Typical Applications

Teflon™ NXT 70 is a fine-cut resin designed for compression molding of blocks and sheets. It can be used for:


- Seal rings
- Valve seats
- Bearing pads
- Linings
- Encapsulations
- Base resin for filled compounds

Processing

Teflon™ NXT 70 may be converted by compression molding techniques. A preform made at room temperature at the recommended pressure of 14 MPa (2,000 psi) can subsequently be sintered. Refer to the typical property data in Table 1.

Of particular significance for sheet molding is the fact that maximum density after sintering is reached at lower pressures when compared with non-modified granular grades as shown in Figure 1. This allows for the production of larger sheets with existing equipment.

Figure 1. Effect of Preform Pressure on Standard Specific Gravity

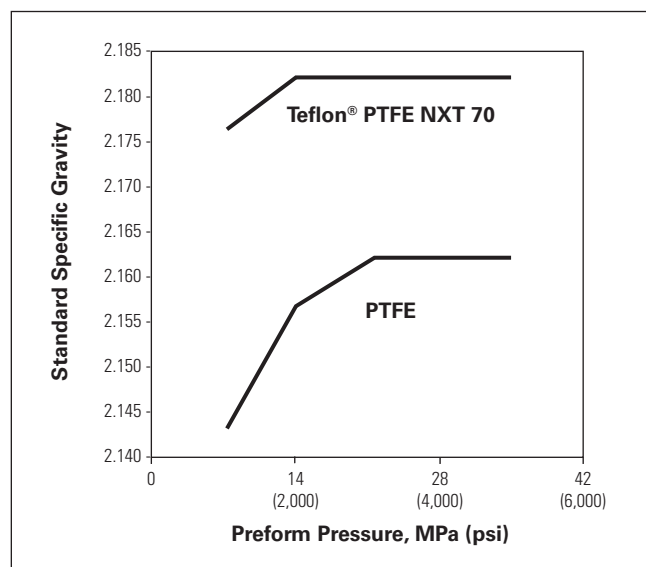

Food Contact Compliance

Properly processed products (sintered at high temperatures common to the industry) made from Teflon™ NXT 70 resin can qualify for use in contact with food in compliance with FDA Regulation 21 CFR 177.1550.

Safety Precautions

Before processing any fluoroplastics, read the Material Safety Data Sheet, available upon request from our Customer Service Group at (844) 773-CHEM/2436 in the U.S. or (302) 773-1000 outside of the U.S. Also read the detailed information in the latest edition of the "Guide to the Safe Handling of Fluoropolymer Resins," published by the Fluoropolymers Division of The Society of the Plastics Industry (www.fluoropolymers.org) or by PlasticsEurope (www.plasticseurope.org).

Storage and Handling

Preforming is easiest when the resin is between 21–27 °C (70–80 °F). As temperature declines below this range, the resin will be increasingly difficult to mold without cracks and problems with condensed moisture. Higher temperatures inhibit flow and promote lumping. Storage conditions should be set accordingly.

Cleanliness is a critical requirement for successful use of Teflon™ NXT 70. The white resin and high sintering temperatures cause even very small foreign particles to become visible in finished moldings.

Keep resin drums closed and clean. Good housekeeping and careful handling are essential.

Packaging

Teflon™ NXT 70 is packaged in 40-kg (88-lb) drums. Each drum has a bag liner made of polyethylene resin.

Table 1. Typical Property Data for Teflon™ PTFE NXT 70 Modified Granular Fluoroplastic Resin*

Property	Test Method	Unit	Typical Value
Average Bulk Density	ASTM D4894	g/L	400
Average Particle Size	ASTM D4894	µm	33
Standard Specific Gravity	ASTM D4894		2.17
Tensile Strength	ASTM D4894	psi (MPa)	5600 (38.6)
Elongation at Break	ASTM D4894	%	550
Deformation Under Load 14 MPa (2,000 psi), 23 °C (73 °F), 24 h	D621 Method A	%	4

Teflon™ PTFE NXT 70 meets the requirements of ASTM D4894-15, Type III, Grade 1.

*Typical properties are not suitable for specification purposes.

HOW TO USE THE TEFLON™ BRAND NAME WITH YOUR PRODUCT

Teflon™ is a registered trademark of Chemours for its brand of fluoroplastic resins, coatings, films, and dispersions. The Teflon™ brand name is licensed by Chemours in association with approved applications. Without a trademark license, customers may not identify their product with the Teflon™ brand name, as Chemours does not sell such offerings with the Teflon™ trademark. Unlicensed customers may refer to the Chemours product offering with only the Chemours name and product code number descriptor as Chemours sells its product offerings. There are no fair use rights or exhaustion of rights to use the Teflon™ trademark from buying from Chemours, a Chemours customer, or a distributor without a trademark license from Chemours.

If you are interested in applying for a trademark licensing agreement for the Teflon™ brand, please visit www.teflon.com/license

CAUTION: Do not use Chemours materials in medical applications involving permanent implantation in the human body or contact with bodily fluids or tissues, unless the material has been provided from Chemours under a written contract that is consistent with Chemours policy regarding medical applications and expressly acknowledges the contemplated use. For further information, please contact your Chemours representative. You may also visit www.teflon.com/industrial to download a copy of the "Chemours POLICY Regarding Medical Applications" and "Chemours CAUTION Regarding Medical Applications." For medical emergencies, spills, or other critical situations, call (866) 595-1473 within the United States. For those outside of the United States, call (302) 773-2000.

The information set forth herein is furnished free of charge and based on technical data that Chemours believes to be reliable. It is intended for use by persons having technical skill, at their own discretion and risk. The handling precaution information contained herein is given with the understanding that those using it will satisfy themselves that their particular conditions of use present no health or safety hazards. Because conditions of product use are outside our control, Chemours makes no warranties, express or implied, and assumes no liability in connection with any use of this information. As with any material, evaluation of any compound under end-use conditions prior to specification is essential. Nothing herein is to be taken as a license to operate under or a recommendation to infringe any patents.

NO PART OF THIS MATERIAL MAY BE REPRODUCED, STORED IN A RETRIEVAL SYSTEM OR TRANSMITTED IN ANY FORM OR BY ANY MEANS ELECTRONIC, MECHANICAL, PHOTOCOPYING, RECORDING OR OTHERWISE WITHOUT THE PRIOR WRITTEN PERMISSION OF CHEMOURS.

For more information, visit teflon.com/industrial

For sales and technical support contacts, visit teflon.com/industrialglobalsupport

© 2015 The Chemours Company FC, LLC. Teflon™ and any associated logos are trademarks or copyrights of The Chemours Company FC, LLC. Chemours™ and the Chemours Logo are trademarks of The Chemours Company.

Replaces: K-27445

C-10143 (11/15)